

A Mathematical Model for the Flexural Strength Characteristics of Concrete Made with Unwashed Local Gravel Using the Second- Degree Polynomial

Umeonyiagu Ikechukwu Etienne¹, Adinna B.O. ²

¹Dept. of Civil Engineering, Anambra State University, P.M.B.02,Uli

²Dept. of Civil Engineering, Nnamdi Azikiwe University, Awka

E-mail- umeonyiaguichechukwu@yahoo.com

ABSTRACT: This research work set out to develop a model for the flexural strength characteristics of concrete made with unwashed local aggregate based on the second-degree polynomial. The unwashed local gravel was from Abagana and the river sand from Amansea, both in Anambra State of Nigeria. These aggregates were tested for their physical and mechanical properties based on BS 812: Part 2 & Part 3:1975. Sixty concrete beams of dimensions 150 mm X 150mm X 600mm—three beams for each experimental point were made, cured and tested according to BS 1881:1983. The model equation developed was $\hat{Y} = -366.27Z_1 + 249.99Z_2 - 15.93Z_3 - 20.24Z_4 + 18.68Z_1Z_2 - 1675.23Z_1Z_3 + 605.84Z_1Z_4 + 1458.06Z_2Z_3 - 290.71Z_2Z_4 + 78.14Z_3Z_4$. The student's t-test and the Fisher's test were used to test the adequacy of this model. The strengths predicted by the model were in complete agreement with the experimentally obtained values and the null hypothesis was satisfied.

Key words: Optimization, Concrete, Flexural strength, Second-degree polynomial, Fisher's test, Model, Taylor's theorem.

1. INTRODUCTION

1.1. OSADEBE'S CONCRETE OPTIMIZATION THEORY

Concrete is a four-component material of mixing water, cement, fine and coarse aggregate. These ingredients are mixed in rational proportions to achieve desired strength of the hardened concrete [1]. Let us consider an arbitrary amount, S, of a given concrete mixture and S_i , the portion of the i^{th} component of the four constituent materials of the concrete where $i = 1, 2, 3, 4$, then in keeping with the principle of absolute volume or mass [2]:

$$\sum S_i = S \quad 1$$

Dividing through by S and substituting Z_i for S_i/S gives:

$$\sum Z_i = 1 \quad 2$$

Then, the compressive strength of concrete can be expressed as equation 3:

$$Y = f(Z_i) \tag{3}$$

Using Taylor's theorem and the assumption that Y is continuous, equation 3 becomes:

$$f(Z) = f(Z^{(0)}) + \sum_{i=1}^4 \frac{\partial f(Z^{(0)})}{\partial Z_i} (Z_i - Z_i^{(0)}) + \frac{1}{2!} \sum_{i=1}^3 \sum_{j=1}^4 \frac{\partial^2 f(Z^{(0)})}{\partial Z_i \partial Z_j} (Z_i - Z_i^{(0)}) (Z_j - Z_j^{(0)}) + \frac{1}{2!} \sum_{i=1}^3 \frac{\partial^2 f(Z^{(0)})}{\partial Z_i^2} (Z_i - Z_i^{(0)})^2 + \dots \tag{4}$$

If $b_0 = f(0)$, $b_i = \partial f(0) / \partial Z_i$, $b_{ij} = \partial^2 f(0) / \partial Z_i \partial Z_j$ and $b_{ii} = \partial^2 f(0) / \partial Z_i^2$, then eqn. 4 can be written as follows:

$$f(Z) = b_0 + \sum_{i=1}^4 b_i Z_i + \sum_{i=1}^3 \sum_{j=1}^4 b_{ij} Z_i Z_j + \sum_{i=1}^4 b_{ii} Z_i^2 + \dots \tag{5}$$

Multiplying eqn.2 by b_0 we have

$$b_0 Z_i = b_0 \tag{6}$$

Also, multiplying eqn. 2 by Z_1, Z_2, Z_3 and Z_4 in succession, making Z_1^2, Z_2^2, Z_3^2 and Z_4^2 the subject of the formula, substituting into eqn. 5 and factorizing gives:

$$Y = \sum \beta_i Z_i + \sum \beta_{ij} Z_i Z_j \tag{7}$$

where $\beta_i = b_0 + b_i + b_{ii}$ and $\beta_{ij} = b_{ij} - b_{ii} + b_{jj}$ ($i, j = 1,2,3,4$)

1.2 THE COEFFICIENTS OF THE REGRESSION EQUATION

If the K^{th} response (compressive strength for the serial number k) is $y^{(k)}$, substituting the vector of the corresponding set of variables, i.e., $Z^{(K)} = [Z_1^{(K)}, Z_2^{(K)}, Z_3^{(K)}, Z_4^{(K)}]^T$ (see Table 1) into eqn.7 generates the explicit matrix of equation 8:

$$[y^{(k)}] = [B][Z] \tag{8}$$

Re-arranging eqn.8 yields:

$$[Z]^T [B]^T = [y^{(k)}] \tag{9}$$

Solution of eqn.9 gives the values of the unknown coefficients of the regression equation (eqn 7).

1.3 THE STUDENT'S t-TEST

The unbiased estimate of the unknown variance S^2 is given by [3],

$$S_y^2 = \frac{\sum (y_i - \bar{y})^2}{n - 1} \quad 10$$

If $a_i = z_i (2z_i - 1)$, $a_{ij} = 4 z_i z_j$; for $(1 \leq i \leq q)$ and $(1 \leq j \leq q)$ respectively.

$$\text{Then, } \varepsilon = \sum a_i^2 + \sum a_{ij}^2 \quad 11$$

where ε is the error of the predicted values of the response.

The t-test statistic is given in [3]

$$t = \left(\frac{\Delta y \sqrt{n}}{S_y} \right) \sqrt{(1 + \varepsilon)} \quad 12$$

where $\Delta y = y_0 - y_t$; y_0 = observed value, y_t = theoretical value; n = number of replicate observations at every point; ε = as defined in eqn.11.

1.4 THE FISHER'S TEST

The Fishers-test statistic is given by

$$F = \frac{S_1^2}{S_2^2} \quad 13$$

The values of S_1 (lower value) and S_2 (upper value) are calculated from equation 10.

2. MATERIALS AND METHOD

2.1 PREPARATION, CURING AND TESTING OF CUBE SAMPLES

The aggregates were sampled in accordance with the methods prescribed in BS 812: Part 1:1975 [4]. The test sieves were selected according to BS 410:1986 [5]. The water absorption, the apparent specific gravity and the bulk density of the coarse aggregates were determined following the procedures prescribed in BS 812: Part 2: 1975 [6]. The Los Angeles abrasion test was carried out in accordance with ASTM. Standard C131: 1976 [7]. The sieve analyses of the fine and coarse aggregate samples were done in accordance with BS 812: Part 1: 1975 [4] and satisfied BS 882:1992[8]. The sieving was performed by a sieve shaker. The water used in preparing the experimental samples satisfied the conditions prescribed in BS 3148:1980 [9]. The required concrete specimens were made in threes in accordance with the method specified in BS 1881: 108:1983 [10]. These specimens were cured for 28 days in accordance with BS 1881: Part 111: 1983 [11]. The testing was done in accordance with BS 1881: Part 117:1983 [12] using flexural testing machine.

TABLE 1 SELECTED MIX RATIOS AND COMPONENT'S FRACTION BASED ON OSADEBE'S SECOND DEGREE POLYNOMIAL

S/NO	MIX RATIOS				COMPONENT'S FRACTION			
	S ₁	S ₂	S ₃	S ₄	Z ₁	Z ₂	Z ₃	Z ₄
1	0.88	1	2.5	4	0.105	0.119	0.298	0.477
2	0.86	1	2	4	0.109	0.127	0.254	0.509
3	0.855	1	2	3.5	0.116	0.136	0.272	0.476
4	0.86	1	2	3	0.125	0.146	0.292	0.437
5	0.855	1	2.5	3.5	0.109	0.127	0.318	0.446
6	0.865	1	3	4	0.098	0.113	0.338	0.451
7	0.87	1	3	4.5	0.093	0.107	0.320	0.480
8	0.86	1	1.5	3	0.135	0.157	0.236	0.472
9	0.86	1	2.75	3.4	0.107	0.125	0.343	0.424
10	0.865	1	2	4.25	0.107	0.123	0.246	0.524
CONTROL								
11	0.858	1	2.43	4	0.104	0.121	0.293	0.483
12	0.86	1	1.75	3	0.130	0.151	0.265	0.454
13	0.855	1	2.4	3.5	0.110	0.129	0.309	0.451
14	0.86	1	2	4.33	0.105	0.122	0.244	0.529
15	0.862	1	2.25	3.13	0.119	0.138	0.311	0.432
16	0.858	1	2	2.83	0.128	0.150	0.299	0.423
17	0.858	1	2.67	3.29	0.110	0.128	0.342	0.421
18	0.86	1	3	4.13	0.096	0.111	0.334	0.459
19	0.855	1	2	3	0.125	0.146	0.292	0.438
20	0.8595	1	2.75	4	0.100	0.116	0.319	0.465

LEGEND: S₁= water/cement ratio; S₂=Cement; S₃=Fine aggregate; S₄=Coarse aggregate, Z_i = S_i/S

TABLE 2 Z^TMATRIX

Z ₁	Z ₂	Z ₃	Z ₄	Z ₁ Z ₂	Z ₁ Z ₃	Z ₁ Z ₄	Z ₂ Z ₃	Z ₂ Z ₄	Z ₃ Z ₄
0.105	0.119	0.298	0.477	0.013	0.031	0.050	0.036	0.057	0.142
0.109	0.127	0.254	0.509	0.014	0.028	0.056	0.032	0.065	0.129
0.116	0.136	0.272	0.476	0.016	0.032	0.055	0.037	0.065	0.129
0.125	0.146	0.292	0.437	0.018	0.037	0.055	0.042	0.064	0.127
0.109	0.127	0.318	0.446	0.014	0.035	0.049	0.041	0.057	0.142
0.098	0.113	0.338	0.451	0.011	0.033	0.044	0.038	0.051	0.153
0.093	0.107	0.320	0.480	0.010	0.030	0.045	0.034	0.051	0.154
0.135	0.157	0.236	0.472	0.021	0.032	0.064	0.037	0.074	0.111
0.107	0.125	0.343	0.424	0.013	0.037	0.046	0.043	0.053	0.146
0.107	0.123	0.246	0.524	0.013	0.026	0.056	0.030	0.065	0.129

TABLE 3 RESPONSES OF THE MIX RATIOS

S/NO	S ₁	S ₂	S ₃	S ₄	RESPONSES[N/mm ²]
1	0.88	1	2.5	4	2.51
2	0.86	1	2	4	2.61
3	0.855	1	2	3.5	2.77
4	0.86	1	2	3	2.91
5	0.855	1	2.5	3.5	2.75
6	0.865	1	3	4	1.96
7	0.87	1	3	4.5	1.85
8	0.86	1	1.5	3	3.16
9	0.86	1	2.75	3.4	2.82
10	0.865	1	2	4.25	2.56

LEGEND: S₁= water/cement ratio; S₂=Cement; S₃=Fine aggregate; S₄=Coarse aggregate

2.2 TESTING THE FIT OF THE QUADRATIC POLYNOMIALS

The polynomial regression equation developed was tested to see if the model agreed with the actual experimental results. The null hypothesis was denoted by H_0 and the alternative by H_1 .

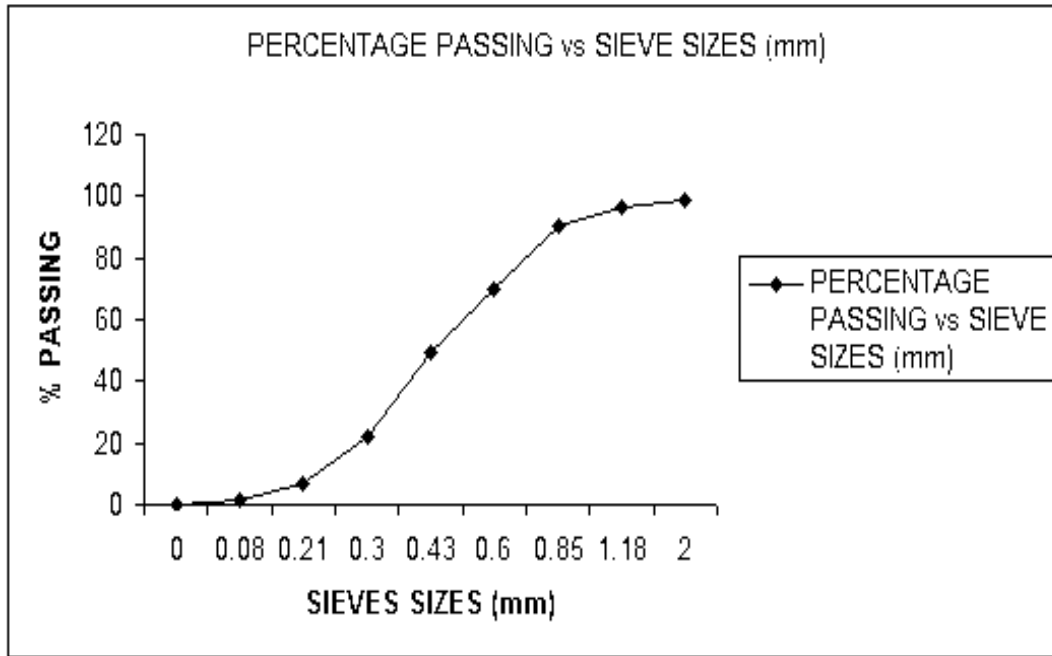


FIGURE 1 GRADING CURVE FOR THE FINE AGGREGATE

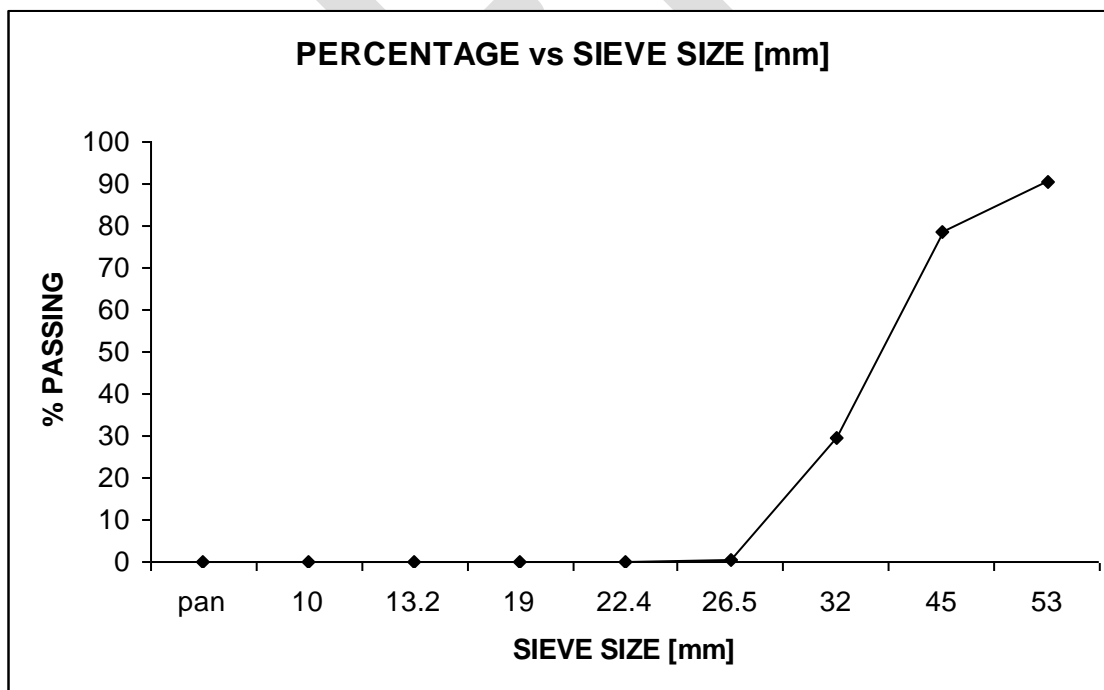


FIGURE 2 GRADING CURVE FOR THE UNWASHED LOCAL GRAVEL

3. RESULTS AND DISCUSSION

3.1 PHYSICAL AND MECHANICAL PROPERTIES OF AGGREGATES

Sieve analyses of both the fine and coarse aggregates were performed and the grading curves shown in Figures 1 and 2. These grading curves showed the particle size distribution of the aggregates. The maximum aggregate size for the local gravel was 53 mm and 2mm for the fine sand. The local gravel had water absorption of 4.55%, moisture content of 53.25%, apparent specific gravity of 1.88, Los Angeles abrasion value of 60% and bulk density of 1302.7 kg/m³.

3.2 THE REGRESSION EQUATION FOR THE COMPRESSIVE STRENGTH TESTS RESULTS

Solution of Eqn.9, given Z^T values of Table 2 and the responses (average flexural strengths) in Table 3 gave the values of the unknown coefficients of the regression equation (Eqn.7) as follows: $\beta_1 = -366.27$, $\beta_2 = 249.99$, $\beta_3 = -15.93$, $\beta_4 = -20.24$, $\beta_{12} = 18.68$, $\beta_{13} = -1675.23$, $\beta_{14} = 605.84$, $\beta_{23} = 1458.06$, $\beta_{24} = -290.71$, $\beta_{34} = 78.14$. Thus, from Eqn.7, the model equation based on second-degree polynomial was given by: $\hat{Y} = -366.27Z_1 + 249.99Z_2 - 15.93Z_3 - 20.24Z_4 + 18.68Z_1Z_2 - 1675.23Z_1Z_3 + 605.84Z_1Z_4 + 1458.06Z_2Z_3 - 290.71Z_2Z_4 + 78.14Z_3Z_4$, where \hat{Y} represented the flexural strength of the mixture in N/mm².

3.3 FIT OF THE POLYNOMIAL

Selected mix ratios and component's fraction based on Osadebe's second degree polynomial was shown in Table 1. The polynomial regression equation developed — $\hat{Y} = -366.27Z_1 + 249.99Z_2 - 15.93Z_3 - 20.24Z_4 + 18.68Z_1Z_2 - 1675.23Z_1Z_3 + 605.84Z_1Z_4 + 1458.06Z_2Z_3 - 290.71Z_2Z_4 + 78.14Z_3Z_4$ was tested to see if the model agreed with the actual experimental results. There was no significant difference between the experimental and the theoretically expected results. The null hypothesis, H_0 was satisfied.

TABLE 4 t –STATISTIC FOR THE CONTROLLED POINTS, UNWASHED LOCAL GRAVEL CONCRETE FLEXURAL TEST, BASED ON OSADEBE’S SECOND –DEGREE POLYNOMIAL

RESPONSE SYMBOL	I	j	a_i	a_{ij}	a_i^2	a_{ij}^2	ϵ	\check{y}	\hat{Y}	t
C ₁	1	2	-0.082	0.050	0.007	0.003	0.4835	3.03	3.17	-0.2069
	1	3	-0.082	0.121	0.007	0.015				
	1	4	-0.082	0.120	0.007	0.0399				
	2	3	-0.092	0.142	0.01	0.020				
	2	4	-0.092	0.233	0.013	0.0543				
	3	4	-0.121	0.566	0.016	0.3202				
	4	—	-0.017	—	0.001	—				
				Σ	0.052	0.4316				
	Similarly									
C ₂	—	—	—	—	—	—	0.4809	3.09	3.03	0.09253
C ₃	—	—	—	—	—	—	0.9234	3.05	3.22	-0.2824
C ₄	—	—	—	—	—	—	0.4642	3.08	3.19	-0.15354
C ₅	—	—	—	—	—	—	0.5053	2.55	2.44	0.15628
C ₆	—	—	—	—	—	—	0.4966	2.98	2.73	0.37210
C ₇	—	—	—	—	—	—	0.5707	2.77	2.55	0.32260
C ₈	—	—	—	—	—	—	0.5624	2.48	2.75	-0.40003
C ₉	—	—	—	—	—	—	0.4949	2.97	3.20	-0.34129
C ₁₀	—	—	—	—	—	—	0.5236	2.81	2.88	-0.10948

LEGEND: c_i =response; a_i = z_i (2z_i - 1); a_{ij} = 4 z_iz_j; $\epsilon = \Sigma a_i^2 + \Sigma a_{ij}^2$; \check{y} = experimentally-observed value; \hat{Y} = theoretical value; t = t-test statistic

3.4 t -VALUE FROM TABLE

The student’s t-test had a significance level, $\alpha = 0.05$ and $t_{\alpha/1(ve)} = t_{0.005(9)} = 3.69$ from the standard table [13]. This was greater than any of the t values calculated in Table 4. Therefore, the regression equation for the unwashed gravel concrete was adequate.

3.5 F-STATISTIC ANALYSIS

The sample variances S_1^2 and S_2^2 for the two sets of data were not significantly different (Table 5). It implied that the error(s) from experimental procedure were similar and that the sample variances being tested are estimates of the same population variance. Based on eqn.10, we had that $S_K^2 = 9.647/9 = 1.072$, $S_E^2 = 10.428/9 = 1.159$ & $F = 1.072/1.159 = 0.925$. From Fisher’s table[13], $F_{0.95(9,9)} = 3.3$, hence the regression equation for the flexural strength of the unwashed gravel concrete was adequate.

TABLE 5 F –STATISTIC FOR THE CONTROLLED POINTSBASED ON OSADEBE’S SECOND –DEGREE POLYNOMIAL

Response symbol	Y_K	Y_E	$Y_K - \check{Y}_K$	$Y_E - \check{Y}_E$	$(Y_K - \check{Y}_K)^2$	$(Y_E - \check{Y}_E)^2$
C_1	3.03	3.17	-0.812	-0.729	0.659	0.532
C_2	3.09	3.03	-0.748	-0.871	0.559	0.759
C_3	3.05	3.22	-0.787	-0.676	0.619	0.458
C_4	3.08	3.19	-0.761	-0.715	0.579	0.511
C_5	2.55	2.44	-1.289	-1.456	1.662	2.119
C_6	2.98	2.73	-0.856	-1.171	0.733	1.370
C_7	2.77	2.55	-1.074	-1.349	1.153	1.821
C_8	2.48	2.75	-1.361	-1.153	1.852	1.330
C_9	2.97	3.20	-0.872	-0.698	0.760	0.487
C_{10}	2.81	2.88	-1.035	-1.021	1.071	1.041
Σ	28.806	29.161			9.647	10.428

Legend: $\check{Y} = \Sigma Y/n$ where y is the response and n, the number of observed data (responses)
 Y_k is the experimental value (response)
 Y_E is the expected or theoretically calculated value(response)

CONCLUSION

The strengths (responses) of concrete were a function of the proportions of its ingredients: water, cement, fine aggregate and coarse aggregates. Since the predicted strengths by the model were in total agreement with the corresponding experimentally -observed values, the null hypothesis was satisfied. This meant that the model equation was valid.

REFERENCES:

[1] Neville, A. M., *Properties of Concrete, Third Edition*, Pitman, London, 1995, pp.268-358.
 [2] Osadebe, N.N., *Generalised Mathematical Modelling of Compressive Strength of Normal Concrete as a Multivariant function of the properties of its constituent components*, Lecture, University of Nigeria, Nsukka, 2003, pp.1 – 11.
 [3] Biyi, A., *Introductory Statistics*, Abiprint& Pak Ltd., Ibadan, 1975, pp.89 – 120.
 [4] BS 812: Part 1 *Sampling, shape, size and classification*. Methods for sampling and testing of mineral aggregates, sands and fillers. British Standards Institution Publication, London, 1975, pp. 2 – 5.
 [5] BS 410 *Specification for test sieves*. British Standards Institution Publication, London, 1986, pp. 1 – 4.

- [6] BS 812: Part 2 Methods for sampling and testing of mineral aggregates, sands and fillers. *Physical properties*. British Standards Institution Publication, London, 1975, pp. 2 – 6.
- [7] ASTM. Standard C 131 *Tests for Resistance to Abrasion of Small Size Coarse Aggregate by Use of the Los Angeles Machine*. American Society for Testing and Materials Publication, New York, 1976, 1 – 6.
- [8] BS 882 *Specification for aggregates from natural sources for concrete*. British Standards Institution Publication, London, 1992, pp.2 – 6.
- [9] BS 3148 *Tests for water for making concrete*. British Standards Institution Publication, London, 1980, pp. 1 – 8.
- [10] BS 1881: Part 108 *Method formaking test cubes from fresh concrete*. British Standards Institution Publication, London, 1983, pp. 1 – 4.
- [11] BS 1881: Part 111 *Method of normal curing of test specimens (20 °C)*. British Standards Institution Publication, London, 1983, pp.1 – 5.
- [12] British Standard 1881: Part 117 *Method for determination of flexural strength of concrete cubes*. British Standards Institution Publication, London, 1983, pp.1 – 6.
- [13] Nwaogazie, I.L., *Probability and Statistics for Science and Engineering Practice*, University of Port Harcourt Press, Port Harcourt, 2006, pp. 274 – 280